

Trifluoromethylation of carbonyl groups in aromatic poly(ether ketone)s: formation of strongly polar yet surface-hydrophobic poly(arylenecarbinol)s

Article

Accepted Version

Leroux, F., Bennett, R. ORCID: <https://orcid.org/0000-0001-6266-3510>, Lewis, D. and Colquhoun, H. M. (2018)
Trifluoromethylation of carbonyl groups in aromatic poly(ether ketone)s: formation of strongly polar yet surface-hydrophobic poly(arylenecarbinol)s. *Macromolecules*, 51 (9). pp. 3415-3422. ISSN 0024-9297 doi: 10.1021/acs.macromol.8b00017
Available at <https://centaur.reading.ac.uk/77256/>

It is advisable to refer to the publisher's version if you intend to cite from the work. See [Guidance on citing](#).

Published version at: <https://pubs.acs.org/doi/10.1021/acs.macromol.8b00017>

To link to this article DOI: <http://dx.doi.org/10.1021/acs.macromol.8b00017>

Publisher: American Chemical Society

All outputs in CentAUR are protected by Intellectual Property Rights law, including copyright law. Copyright and IPR is retained by the creators or other copyright holders. Terms and conditions for use of this material are defined in the [End User Agreement](#).

www.reading.ac.uk/centaur

CentAUR

Central Archive at the University of Reading

Reading's research outputs online

Trifluoromethylation of carbonyl groups in aromatic poly(ether ketone)s: formation of strongly polar yet surface-hydrophobic poly(arylenecarbinol)s

*Flavien Leroux, Roger A. Bennett, David F. Lewis and Howard M. Colquhoun**

Department of Chemistry, University of Reading, Whiteknights, Reading, RG6 6AD, UK

Abstract: Fluoride-catalyzed reactions of trimethyl(trifluoromethyl)silane with a range of aromatic poly(ether ketone)s, both amorphous and semi-crystalline, proceed quantitatively in THF to yield soluble, amorphous polymers in which the carbon-silicon bond of CF_3SiMe_3 has added across the carbonyl-oxygen double bond of each carbonyl group. When the starting poly(ether ketone) is amorphous and soluble in THF the reaction is fairly rapid (hours), but is much slower (days) when the starting polymer is semi-crystalline, with only low solubility in THF. Quantitative desilylation of the resulting polymers is achieved by reaction with excess fluoride ion, affording poly(arylene-trifluoromethylcarbinol)s. These extremely polar polymers are readily soluble in protic solvents such as methanol or ethanol, to give solutions from which tough, coherent films may be cast by evaporation in air. Despite the evidently high polarity of the bulk polymers, the surfaces of cast films are relatively hydrophobic, with static water contact angles of $\sim 90^\circ$. Surface analyses by XPS are consistent with enrichment of the polymer-air interface in CF_3 groups.

Introduction

Semicrystalline aromatic poly(ether ketone)s represent an industrially-important class of high-performance thermoplastics with outstanding physico-chemical properties.¹ For example, PEEK (Chart 1) is widely used in situations that require mechanical strength at very high temperatures,² or in chemically aggressive environments,³ or in applications such as medical implants and prostheses which exploit its inert character and biocompatibility.⁴ It also finds increasing application as a thermoplastic matrix in high-performance carbon fibre composites.⁵

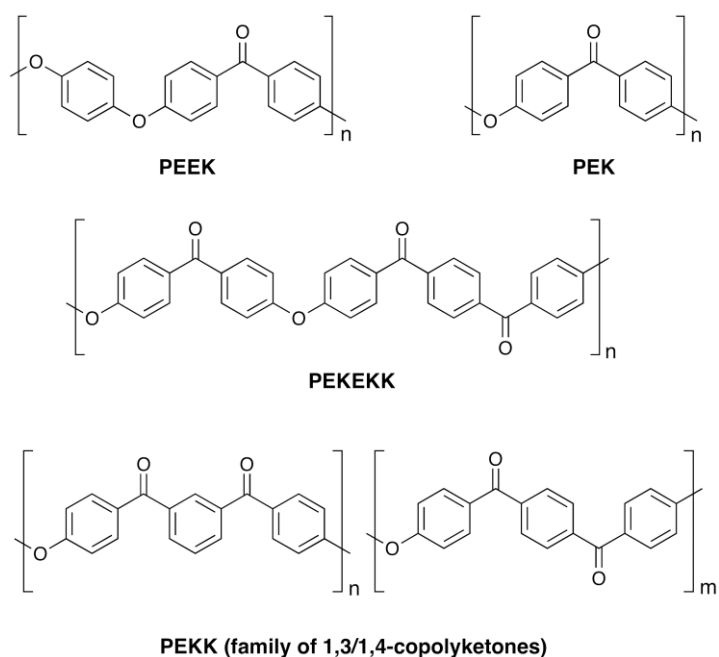


Chart 1. Some industrially important poly(aryl ether ketone)s


Several post-synthesis derivatization reactions of semi-crystalline poly(ether ketone)s have been described, though the insolubility of the latter in conventional solvents precludes the application of many types of chemistry.⁶ Nevertheless, PEEK may be sulfonated selectively at the hydroquinone residue simply by dissolving it in concentrated sulfuric acid.⁷ The resulting

polysulfonate ionomer (depending on the degree of sulfonation) may then be soluble in polar aprotic solvents such as *N,N*-dimethylformamide or *N,N*-dimethylacetamide.⁷ However, this type of chemistry is far from general in that many important poly(ether ketone)s such as PEK, PEKEKK and PEKK (Chart 1), in which every ring carries at least one deactivating carbonyl group, dissolve in but are essentially inert to concentrated (96-98%) sulfuric acid.⁸ Nitration of PEEK (again occurring at the hydroquinone residue) has been achieved both homogeneously in strong acid solution,⁹ and also in suspension in so-called mixed acid (4:1 v/v nitric:sulfuric).¹⁰ Other derivatization chemistries involve reactions at the carbonyl groups, for example reduction by triethylsilane and strong acid to yield poly(ether methylene)s,¹¹ reduction with sodium borohydride to give poly(carbinol)s,¹² iminization with high-boiling primary amines,¹³ and perhaps most successfully the reversible formation of poly(dithioketal)s by reaction with aliphatic dithiols in the presence of a Lewis acid.^{14,15}

The insolubility of semi-crystalline poly(ether ketone)s in conventional organic solvents has also allowed the development of a wide range of *surface*-derivatized materials. Such reactions include reduction with borohydride to yield surface-hydroxylated PEEK,¹⁶ which may be further functionalised by ATRP to graft hydrophilic poly(ethyleneglycol) methacrylate chains onto the surface.¹⁷ Most recently it has been reported that PEEK may be surface-fluorinated by a process involving argon plasma treatment followed by contact with aqueous HF.¹⁸ The resulting polymer showed enhanced antibacterial properties and improved compatibility with stem cells, but the nature of the surface chemistry involved in this type of fluorination was not established.

Here we report the exploration of a novel, fully-defined approach to the introduction of fluorinated groups into aromatic poly(ether ketone)s by a process involving the quantitative addition of trifluoromethyl(trimethyl)silane¹⁹ to the carbonyl groups.²⁰ This nucleophilic

trifluoromethylation reaction (Scheme 1) is well-established in small-molecule chemistry,²¹ but has not been applied previously to the functionalization of macromolecules.

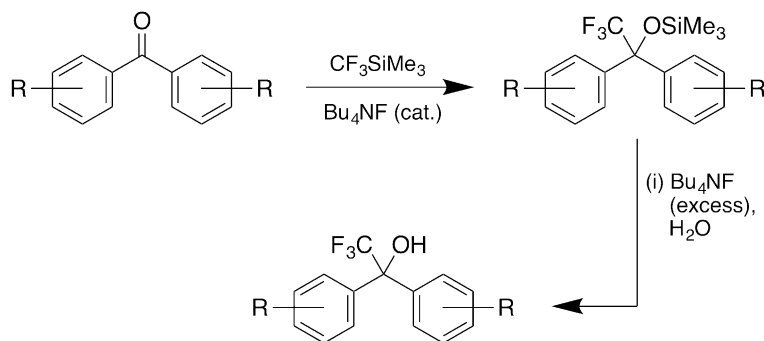

Scheme 1. Conversion of an aromatic ketone to a trifluoromethylcarbinol via the trimethylsilyl ether derivative, by fluoride-catalyzed addition of CF_3SiMe_3 to the carbonyl group.^{20,21}

It is well-established that fluorocarbon moieties in polymeric systems tend to segregate at the polymer-air interface, giving rise to low-energy, hydrophobic surfaces.²² Such systems include poly(perfluoroalkyl methacrylate) homopolymers and copolymers,^{23,24} di- and tri-block copolymers containing one highly fluorinated block,^{25,26} anionically-polymerised polyalkenes such as polystyrene or polybutadiene terminated with a single, short (e.g. $-\text{C}_8\text{F}_{17}$) perfluoroalkyl chain,^{27,28} and fluorocarbon-grafted polymers such as those formed by difluorocarbene addition to the double bonds of poly(isoprene).^{29,30} The vast majority of these previously-reported systems combine fluorocarbon residues with subunits that are themselves relatively hydrophobic (typically having hydrocarbon, ester or ether functionality). In contrast, the new materials reported here introduce both a strongly hydrophilic hydroxyl group and a strongly hydrophobic trifluoromethyl group at the same backbone carbon atom(s) in every polymer repeat unit, leading to polymers with some unusual physico-chemical characteristics.

Results and discussion

Our initial attempts to apply nucleophilic trifluoromethylation chemistry to highly crystalline and insoluble poly(ether ketone)s such as PEEK and PEK (Chart 1) in suspension in THF failed to afford any reaction, even with very finely-divided polymer powders (<50 μm). We next investigated a series of THF-soluble or -swellable, poly(ether ketone)s (**1–4**, Chart 2) that were synthesised at high molecular weight from monomers **5–9** using conventional polyetherification chemistry.³¹ These polymers were designed to provide widely different ketone contents and thus, potentially, to afford fluorinated polyols with a range of equivalent weights in terms of trifluoromethylcarbinol units. Polymers **1** and **2** are known to be amorphous,³² and although polymer **4** is semi-crystalline, it has a relatively low melting point (310 $^{\circ}\text{C}$)³³ and was thus predicted to be more soluble and reactive than PEEK or PEK. Neither monomer **8** nor polymer **3** (which also proved to be amorphous) have been reported previously, but the discovery in this work of a novel "extended Fries" rearrangement (Scheme 2) allowed monomer **8** to be obtained in good yield and purity. Polymers **1–4** were synthesised by polycondensation at high temperature in either NMP or diphenylsulfone as solvent, as described in the Supporting Information (SI) where full characterisation data are also given.

Polyketones **1** and **2** were fully soluble in THF and reacted cleanly with trifluoromethyl(trimethyl)silane in the presence of catalytic amounts of tetra-*n*-butylammonium fluoride to afford, after 18 h, the trifluoromethylated polymers **10** and **11** in 82% and 70% yields respectively (Chart 3). Polymers **3** and **4** did not dissolve in THF, though the amorphous, dibenzofuran-based polymer **3** swelled significantly in this solvent. Nevertheless, it was found that **3** and **4** could be successfully trifluoromethylated over a much longer period (120 h) by

repeated addition of $\text{CF}_3\text{Si}(\text{CH}_3)_3$ and Bu_4NF at 24 h intervals, ultimately giving polymers **12** and **13** in 80% and 75% yields respectively (Chart 3).


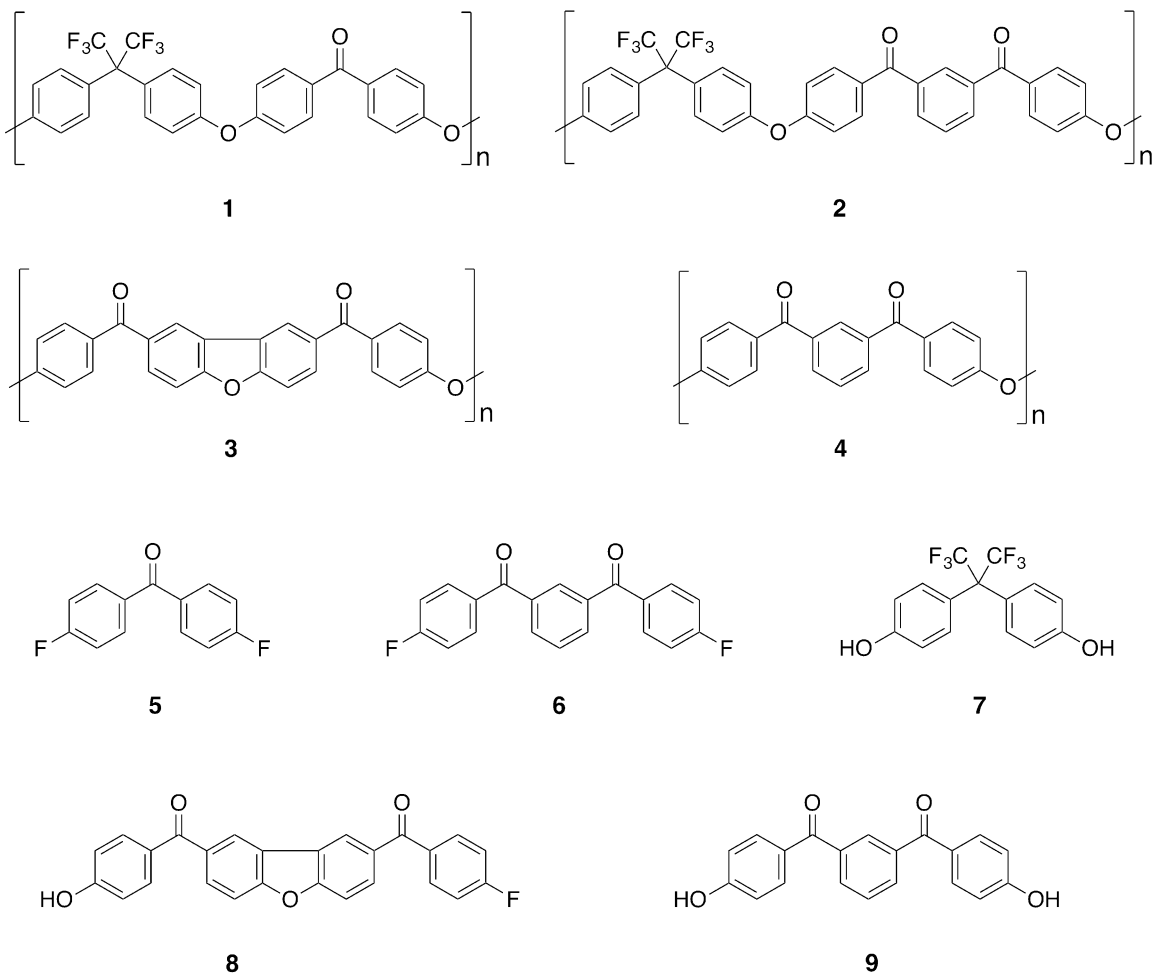


Chart 2. Poly(arylene ether ketone)s **1–4**, synthesised in the present work using monomers **5–9**.

All four trimethylsilyl polymers, **10–13**, proved readily soluble in THF, and subsequent GPC analyses in this solvent showed number average molecular weights M_n in the range 15 – 59 kDa, with dispersities between 1.9 and 2.9. Full characterization details are given in the SI.

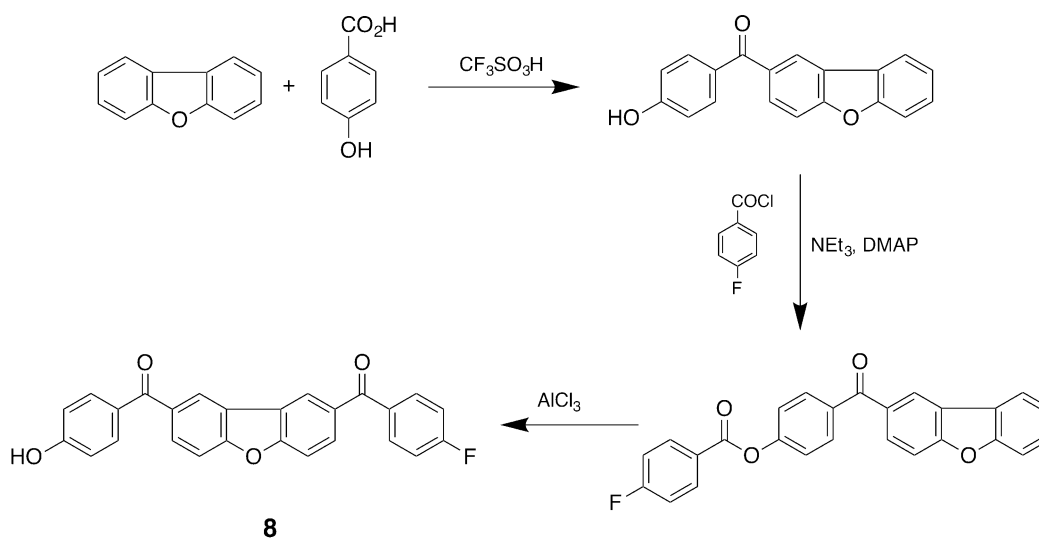

Scheme 2. Synthesis of monomer **8** from dibenzofuran via sequential hydroxybenzoylation, esterification and "extended-Fries" rearrangement of the ester in triflic acid. Like the standard Fries "rearrangement", the latter is almost certainly a bimolecular Friedel-Crafts type reaction in which an oxyaryl group (here the dibenzofuran residue) of one ester molecule is aroylated by a second molecule of the ester.

An intriguing feature of the ^1H NMR spectra of both isophthaloyl-derived polymers **11** and **13** is that the aromatic proton lying between the two trifluoromethylated carbons gives rise to two resonances of similar (but not equal) intensity (Figure 1). These resonances arise from the stereochemistries of the two adjacent $[\text{Ar}(\text{Ar}')\text{C}(\text{CF}_3)\text{OSiMe}_3]$ groups which, being chiral, may combine as RS, SR, SS, or RR. The polymer repeat unit is thus diastereomeric, and the two observed ^1H resonances in the spectra of **11** and **13** result from magnetic inequivalence of the pairs of enantiomeric stereocentres RS/SR and RR/SS (Figure 2). Since diastereomers have different free energies of formation, the inequality of the two populations, as indicated by NMR (Figure 1), is not unexpected. Indeed, molecular mechanics calculations on model compounds suggest that, of the two enantiomeric pairs, the RS/SR diastereomeric pair is some 10% lower in energy than its SS/RR counterpart, a value that is compatible with the observed difference in intensity between the corresponding ^1H NMR resonances. See SI for details of these calculations.

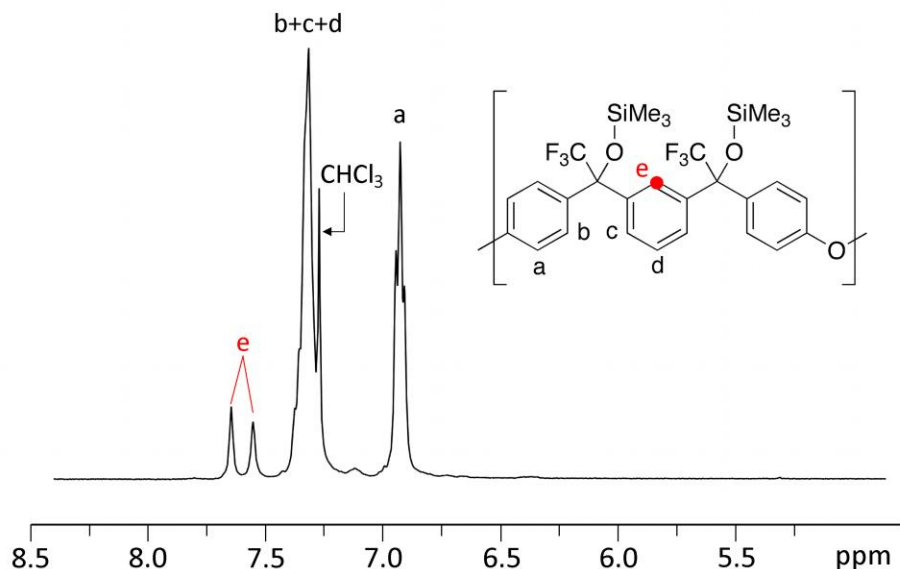


Figure 1. ^1H NMR spectrum of polymer **13** in the aromatic region, showing the two resonances arising from the single aromatic proton (e) adjacent to both trifluoromethylated carbons.

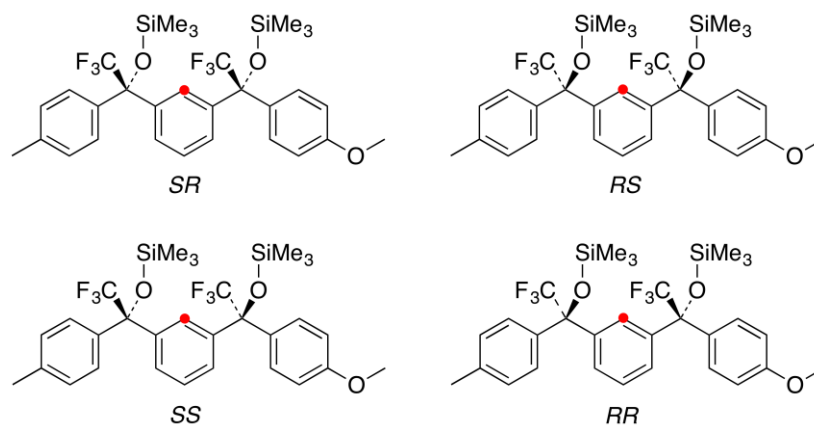


Figure 2. Diastereomeric pairs of chiral units in polymers **11** and **13**.

Desilylation of polymers **10–13** was achieved by reaction with a large molar excess of tetra-*n*-butylammonium fluoride hydrate in THF, and the resulting trifluoromethyl polyols **14–17** were purified by reprecipitation in water from acetone solution and isolated in 50 – 75% yields. The ^1H NMR spectrum of polymer **15** is shown in Figure 3, which again shows diastereomeric effects

in the splitting of the resonance due to the proton (g) located between the two trifluoromethylated carbons. The remarkably high resolution of this spectrum (for a high molecular weight polymer) enables all seven different proton environments in the polymer to be assigned as shown (see also SI). This spectrum also demonstrates the effectiveness of the chemistry in providing a clean, 2-step, conversion of the starting polyketone **2** to the fully trifluoromethylated polyol **15**.

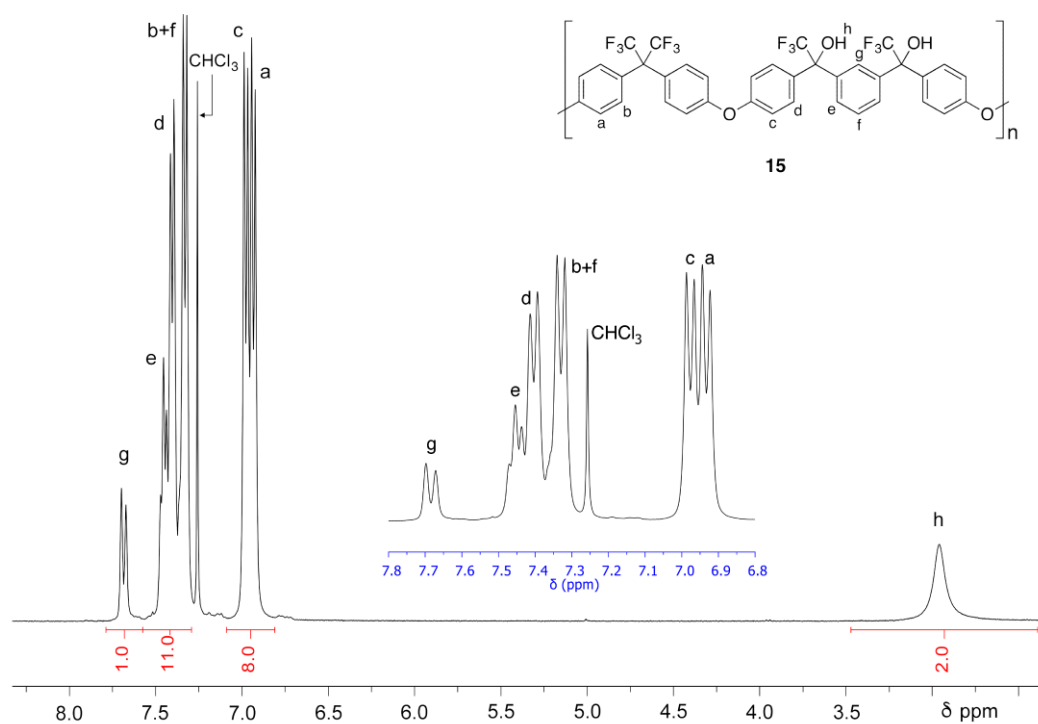


Figure 3. ^1H NMR spectrum of polymer **15** in CDCl_3 , showing the two diastereomer-related resonances arising from the single proton (g) adjacent to both trifluoromethylated carbons, and also a complete assignment of all other resonances. Inset shows an expansion of the aromatic region. See also SI.

The structures of polyols **14** and **15** were confirmed by ^{19}F NMR spectroscopy, which showed resonances corresponding to both the hexafluoroisopropylidene (-64.1 ppm) and trifluoromethylcarbinol (-74.5 ppm) groups. As show in the SI, the relative integrals of these

two resonances correspond very closely to the ratios expected (2:1 and 1:1) from the structures of polymers **14** and **15** respectively, shown in Chart 3.

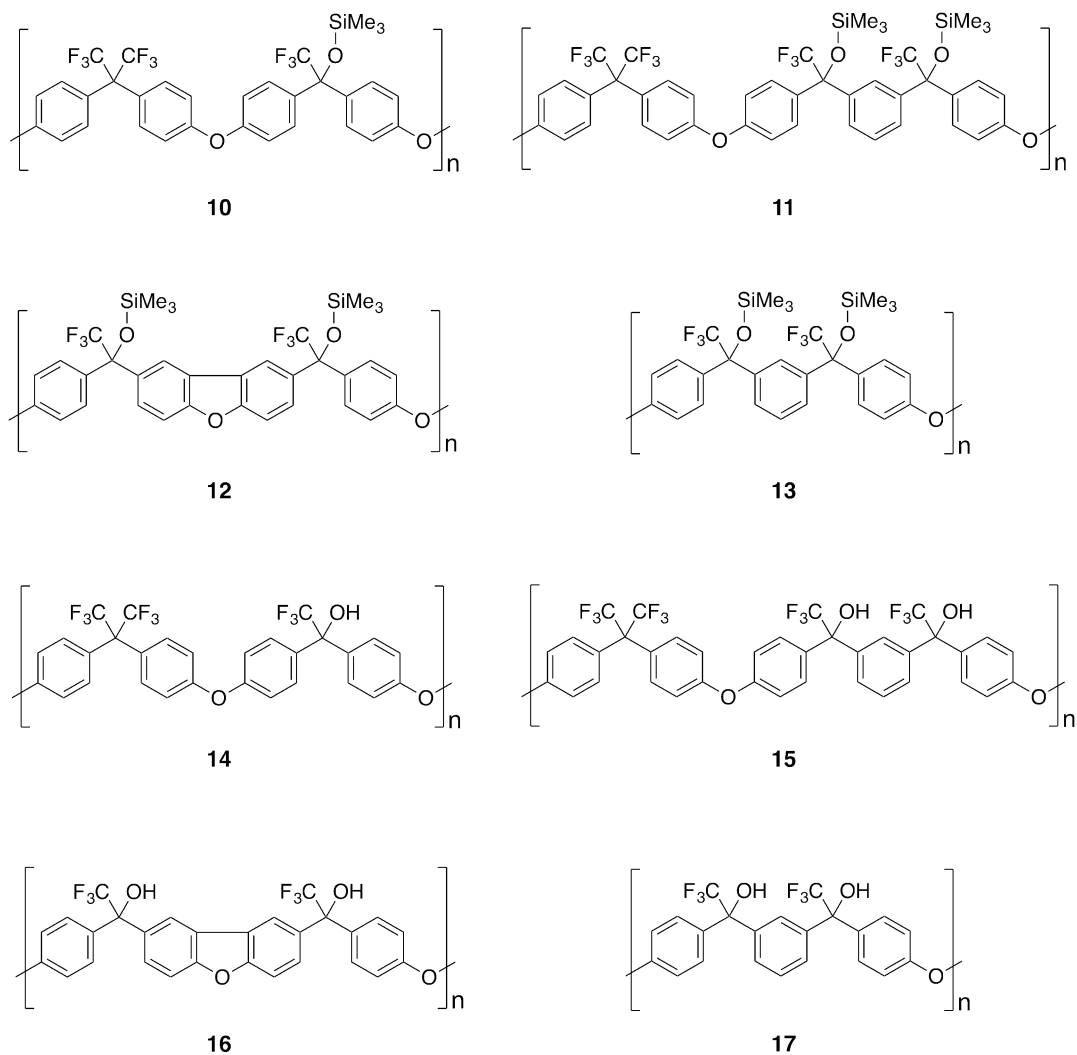


Chart 3. Polymers **10–13** resulting from addition of CF_3SiMe_3 to the carbonyl groups of poly(ether ketone)s **1–4**, and the polycarbinols **14–17** subsequently obtained by desilylation of **10–13**.

Fluoride-promoted desilylation of polymers **10–13** does not lead to degradation of the polymer backbone, as can be seen from the GPC data in Table 1. Indeed, M_w and $\bar{D}$ values found for the desilylated polymers **15**, **16** and **17** are considerable *greater* than those of the parent silylated

polymers, with the effect being most striking for polyols **15** and **17**. The GPC curve for polyol **15** is given in Figure 4, from which it is clear that there are no obvious features such as a bimodal distribution or a distorting shoulder that might account for the anomalously high molecular weight values. The origin of this result is at present unknown, though it may be significant that polyols **15** and **17** are both derived from polyketones based on the isophthaloyl unit. Preliminary computational modelling studies suggest that the MW anomalies could result from inter-chain association involving specific hydrogen bonds between 1,3-related trifluoromethylcarbinol groups, and more extensive investigations of this phenomenon are currently in progress.

Table 1. Characterisation data for polymers **1-4** and **10-17**

Polymer	η_{inh} (dL g ⁻¹)	M_n/M_w (kDa) ^c	Dispersity $\mathcal{D}$	T_g/T_m (°C) ^e
1	0.39 ^a	13.0/23.6	1.97	155/–
2	0.74 ^a	20.4/57.00	2.80	158/–
3	0.64 ^b	d	d	226/–
4	1.13 ^b	d	d	160/258
10	–	21.1/48.8	2.32	152/–
11	–	59.0/136	2.31	127/–
12	–	15.4/44.0	2.86	172/–
13	–	21.2/39.6	1.87	90/–
14	–	15.4/29.8	1.94	155/–
15	–	420/1,640	3.90	143/–
16	–	23.1/86.6	3.75	216/–
17	–	25.0/244	8.96	120/–

^a In NMP; ^b In 96% H₂SO₄; ^c By GPC in THF; ^d Insoluble in THF; ^e By DSC, T_g = midpoint.

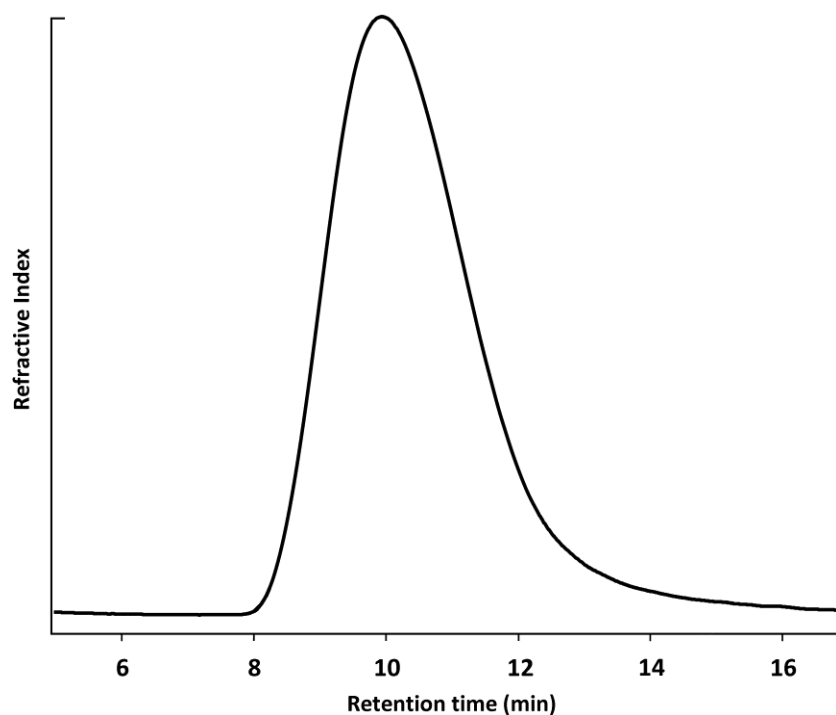


Figure 4. GPC curve for polymer **15** (THF as eluent). See Table 1.

The high polarity of the polyols (**14–17**) obtained in this work was demonstrated by their ready solubility in polar, protic solvents such as methanol, ethanol, 2-methoxyethanol and propan-2-ol, from which tough, coherent films (see SI) may be obtained on evaporation. However, the *surfaces* of such films are notably non-polar, with static water contact angles of ca. 90° – comparable with literature values of 86° for polystyrene,³⁴ and 82° for PEEK.³⁵ Indeed, the contact angle for polyol **15** is essentially identical to that of its precursor polyketone **2** (see SI). This result demonstrates that the hydrophilic hydroxyl groups must be largely excluded from the polymer-air interface,³⁶ leaving a higher proportion of the hydrophobic trifluoromethyl groups at the polymer surface than in the bulk. Indeed, preliminary XPS data for films of polyols **15** and **16** (spin-cast from 2-methoxyethanol), averaged over take-off angles of $25\text{--}60^\circ$, show significant surface-atom enrichment in the carbons associated with CF_3 groups ($\text{C}^*\text{-CF}_3$ and $\text{C-C}^*\text{F}_3$), and a

corresponding depletion in aromatic carbon atoms. Table 2 gives XPS data for polymers **15** and **16**, and the corresponding spectra are given as Supporting Information.

Table 2. XPS data (carbon 1s) for polymers **15** and **16**

Polymer	Atom type	Peak P??????????	FWHM (eV)	Atom concn. found (%)	Atom concn. calcd. (%)	Atom concn. excess (%)
15	C _{aromatic}	284.70	1.634	66.5	81.1	−18.0
	*C−CF ₃	286.75	1.634	15.6	8.1	+92.6
	C−*CF ₃	292.39	1.634	17.9	10.8	+65.7
16	C _{aromatic}	284.45	1.643	74.0	85.8	−13.8
	*C−CF ₃	286.34	1.643	15.2	7.1	+114
	C−*CF ₃	291.95	1.643	10.8	7.1	+52.1

Experimental Section

Materials and Instrumentation.

Starting materials and solvents were purchased from Sigma-Aldrich or Fluorochem and were used as received, with the exception of anhydrous potassium carbonate which was heated at 100 °C under vacuum for 24 h before use, and tetrahydrofuran (THF), which was distilled under argon from sodium and benzophenone. Proton and ¹³C NMR spectra were recorded on either a Bruker Nanobay 400 or a Bruker DPX 400 spectrometer, operating at 400 MHz for ¹H NMR and 100 MHz for ¹³C NMR, respectively. Proton chemical shifts (δ) are reported in ppm relative to tetramethylsilane (δ 0.00 ppm) for CDCl₃ or to the residual solvent peak for acetone-*d*₆ (δ 2.05 ppm) and DMSO-*d*₆ (δ 2.50 ppm). ¹³C NMR chemical shifts are reported relative to chloroform (δ 77.0 ppm), acetone-*d*₆ (δ 29.8 ppm) or DMSO-*d*₆ (δ 39.5 ppm). Fourier transform infrared

(FTIR) spectra were recorded on a Perkin Elmer 100 Spectrum FT-IR using a diamond ATR sampling accessory. Mass spectrometry was carried out using a ThermoFisher Scientific Orbitrap XL LCMS. The sample was introduced by liquid chromatography and sample ionisation was achieved by electrospray ionisation (ESI). Gel permeation chromatography (GPC) was conducted using an Agilent Technologies 1260 Infinity system calibrated with polystyrene standards. Samples were dissolved in analytical grade THF (2 mg mL⁻¹) containing butylated hydroxytoluene (BHT) stabiliser and run using the same solvent as the mobile phase, eluting through two Agilent PLgel 5 μ m MIXED-D 300 $\times$ 7.5 mm columns in series. Phase transitions (glass transitions, cold crystallizations and melting points) were identified by differential scanning calorimetry (DSC) under nitrogen, using a TA Instruments DSC 2920. Inherent viscosities (η_{inh}) were measured at 25 °C with 0.1% w/v polymer solutions in *N*-methyl-2-pyrrolidone (NMP) or 96% sulfuric acid (H₂SO₄) using a Schott Instruments CT 52 viscometer. Polymer films for contact angle measurements were obtained by evaporation of polymer solutions in 2-methoxyethanol (20 mg mL⁻¹) on glass microscope slides. X-ray photoelectron spectroscopy (XPS) was carried out in a custom-modified UHV chamber equipped with an un-monochromated Al-K α (1486.6 eV) X-ray source, hemispherical electron energy analyser (run at 20 eV pass energy) and a sample transfer stage. Polymer films for XPS were spin coated (40 s at 2400 rpm) from 20 μ L droplets of a 1% w/v polymer solution in a mixture of methanol (80%) and propan-2-ol (20%) onto gold-coated quartz microbalance crystals (Inficon 750-1000-G10).

Polymer syntheses. The synthesis of poly(ether ketone) **2** and its conversion to the poly(trifluoromethyl carbinol) **15** are described here to exemplify the chemistry. Full details of syntheses, instrumental analyses, and NMR assignments are given in the Supporting Information.

Polymer 2: Potassium carbonate (0.584 g, 4.23 mmol), NMP (13 mL), toluene (6 mL), 4,4'-(hexafluoroisopropylidene)diphenol (1.345 g, 4.00 mmol) and 1,3-bis(4'-fluorobenzoyl)benzene (1.421 g, 4.00 mmol) were introduced into a 50 mL round-bottom flask fitted with a stirrer, a Dean-Stark trap, a condenser and, a nitrogen inlet and outlet. The temperature was raised to 180 °C and water was removed by azeotropic distillation with toluene over two hours. After 6 hours, the mixture was cooled to room temperature and poured into methanol (150 mL). The precipitated polymer was filtered off, washed with water (2 × 60 mL) and dried at 100 °C *in vacuo*. The polymer was then purified by two successive re-precipitations in methanol (150 mL) from solution in the minimum amount of dichloromethane. After drying at 100 °C *in vacuo*, poly(ether ketone) **2** was obtained as a white solid (1.98 g, 80% yield). T_g (mid-point) = 158 °C. M_n = 20.4 kDa; M_w = 57.0 kDa; D = 2.80; η_{inh} = 0.74 dL g⁻¹ (NMP).

¹H NMR (CDCl₃, 400 MHz): 7.09 (H_b, d, ³J_{bc} = 9 Hz), 7.12 (H_h, d, ³J_{hi} = 9 Hz), 7.23 (H_c, d, ³J_{cb} = 9 Hz), 7.62 (H_o, t, ³J_{om} = 8 Hz), 7.87 (H_i, d, ³J_{ih} = 9 Hz), 7.99 (H_m, d, ³J_{mo} = 8 Hz), 8.17 (H_n, s) ppm.

¹³C NMR (CDCl₃, 100 MHz): 118.3 (C_h), 119.1 (C_b), 128.5 (C_o), 129.0 (C_d), 130.8 (C_n), 132.0 (C_c), 132.2 (C_j), 132.6 (C_i), 133.2 (C_m), 138.0 (C_l), 156.4 (C_a), 160.7 (C_g), 194.5 (C_k) ppm.

Polymer 11: To a stirred solution of poly(ether ketone) **2** (0.506 g, 0.816 mmols of repeat units) in dry THF (20 mL) were added, at 0 °C under nitrogen, trifluoromethyltrimethylsilane (5.20 mL, 35.1 mmol) and tetra-*n*-butylammonium fluoride (80 mg in 0.5 mL of THF, 0.310 mmol). The reaction mixture was stirred at 0 °C for 3 h and was then allowed to warm to 20 °C. After stirring for 18 h at 20 °C, the volatiles were removed *in vacuo* and the polymer was dissolved in the minimum amount of dichloromethane and precipitated in methanol (200 mL). After filtering

off and drying at 100 °C in *vacuo* for 2 h, the polymer was re-precipitated twice in methanol (200 mL) from solution in the minimum amount of dichloromethane. After drying at 100 °C in *vacuo*, the poly[trifluoromethyl(trimethylsilyl)ether] **11** was obtained as a white solid (0.517 g, 70% yield). T_g (mid-point) = 127 °C. M_n = 59.0 kDa; M_w = 136 kDa; D = 2.31.

^1H NMR (CDCl_3 , 400 MHz): -0.096 (H_m , s), 6.89-7.04 (H_b+H_h , m), 7.24-7.44 ($\text{H}_c+\text{H}_i+\text{H}_o+\text{H}_q$, m), 7.52 and 7.63 (H_p , s) ppm.

^{13}C NMR (CDCl_3 , 100 MHz): 0 (C_m), 80.2 (C_l), 116.7 (C_b), 117.6 (C_h), 126.3 -126.6 -126.8 -127.1 ($\text{C}_p+\text{C}_o+\text{C}_q$), 126.7 (C_d), 128.7 (C_i), 130.6 (C_c), 135.1 (C_j), 139.5 (C_n), 154.9 (C_g), 156.4 (C_a) ppm.

Polymer 15: To a stirred solution of the silyl poly(ether) **11** (1.53 g, 1.69 mmols of repeat units) in dry THF (85 mL) was added tetrabutylammonium fluoride (9.50 g in 15 mL of THF, 36.3 mmol) under nitrogen. After 24 h the volatiles were removed in *vacuo* and the polymer was dissolved in the minimum amount of acetone and precipitated in water (300 mL) and was filtered off and dried under vacuum at 100 °C. It was then dissolved in the minimum amount of acetone and re-precipitated in water (300 mL). After drying at 100 °C in *vacuo* over 2 hours, the polymer was re-precipitated twice in water (300 mL), from solution in the minimum amount of acetone. After drying at 100 °C in *vacuo*, the poly(trifluoromethyl)carbinol **15** was obtained as a pale brown solid (1.01 g, 79% yield). T_g (mid-point) = 143 °C. M_n = 420 kDa; M_w = 1,640 kDa; D = 3.90.

Table 3. Solubility characteristics of poly(trifluoromethyl)carbinol **15**

Solvent	Acetone	THF	CHCl_3	CH_2Cl_2	MEK	MeOH	EtOH	i-PrOH
Solubility at 20 °C	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes

^1H NMR (CDCl_3 , 400 MHz): 2.96 (H_m , s), 6.94 (H_b , d, $^3J_\text{bc} = 8$ Hz), 6.98 (H_h , d, $^3J_\text{hi} = 8$ Hz), 7.33 ($\text{H}_\text{c}+\text{H}_\text{q}$, m, $^3J_\text{cb} = 8$ Hz), 7.41 (H_i , m, $^3J_\text{ih} = 8$ Hz), 7.46 (H_o , m, $^3J_\text{oq} = 7$ Hz), 7.67 and 7.70 (H_p , s) ppm.

^{13}C NMR (CDCl_3 , 100 MHz): 79.3 (C_l), 118.1 (C_b), 119.0 (C_h), 126.5 (C_p), 127.9 (C_o), 128.1(C_d), 128.3 (C_q), 129.2 (C_i), 131.8 (C_c), 134.5 (C_j), 139.3 (C_n), 156.5(C_g), 157.3 (C_a) ppm.

Conclusions

Fluoride-catalyzed reactions of trimethyl(trifluoromethyl)silane with aromatic poly(ether ketone)s afford soluble, amorphous polymers in which the carbon-silicon bond of CF_3SiMe_3 has added across the carbonyl-oxygen double bond of each carbonyl group. Subsequent desilylation with excess fluoride ion yields poly(arylene-trifluoromethylcarbinol)s that are readily soluble in high-polarity solvents such as methanol, ethanol, and 2-methoxyethanol, to give solutions from which tough, coherent films may be cast by evaporation in air. Despite the evident polarity of the bulk polymers, the surfaces of these cast films are relatively non-polar, with water contact angles comparable to that of polystyrene.

Supporting Information

Methods and materials, full synthetic details, and characterisation data (PDF) for monomers **8** and **9** and polymers **1-4**, **10-13** and **14-17**. The Supporting Information is available free of charge on the ACS Publications website.

Author Information

Corresponding author

*(H.M.C.) E-mail: h.m.colquhoun@rdg.ac.uk

ORCID

Howard M. Colquhoun: 0000-0002-3725-4085

Notes

The authors declare no competing financial interest.

Acknowledgements

We are grateful to Tahkur Singh Babra for assistance with tensile testing. We thank the Engineering and Physical Sciences Research Council of the UK (EPSRC) for a Platform Grant (EP/L020599/1) and a research grant (GR/K49560/02) in support of this work.

References

1. Hergenrother, P. M. The use, design, synthesis, and properties of high performance/high temperature polymers: an overview. *High Perf. Polym.* **2003**, *15*, 3-45.
2. Liu, L.; Yan, F.; Gai, F.; Xiao, L.; Shang, L.; Li, M.; Ao, Y. In situ determination of mechanical properties for poly(ether ether ketone) film under extreme conditions. *RSC Adv.* **2017**, *7*, 8670–8676.
3. Glover, L. C.; Magay, D. Stilan 1000 – A versatile high performance polymer for hostile environments. *Tech. Papers – Soc. Plast. Eng.* **1976**, *22*, 148–149.

4. Monich, P.; Henriques, B.; de Oliveira, A. P. N.; Souza, J. C. M.; Fredel, M. C. Mechanical and biological behavior of biomedical PEEK matrix composites: A focused review. *Mater. Lett.* **2016**, *185*, 593–597.
5. Liang, Q.; Wu, X. Research status of carbon fiber-reinforced PEEK composites. *Adv. Mater. Res.* **2014**, *834-836*, 225–228.
6. Shukla, D.; Negi, Y. S.; Uppadhyaya, J. S.; Kumar, V. Synthesis and modification of poly(ether ether ketone) and their properties: a review. *Polym. Rev.* **2012**, *52*, 189–228.
7. Shibuya, N.; Porter, R. S. Kinetics of PEEK sulfonation in concentrated sulfuric acid. *Macromolecules* **1992**, *25*, 6495–6499.
8. Colquhoun, H. M.; Taylor, T. M. C. Membranes. *Eur. Pat.* 0382356 B1, **1995**, to North West Water Group plc.
9. Karcha, R. J.; Porter R. S. Preparation and characterization of nitrated poly(aryl ether ketone). *J. Macromol. Sci., Part A: Pure Appl. Chem.* **1995**, *32*, 957–967.
10. Conceição, T. F.; Bertolino, J.R.; Barra, G. M. O, Mireski, S. L.; Joussefa, A. C.; Pires, A. T. N. Preparation and characterization of poly(ether ether ketone) derivatives. *J. Braz. Chem. Soc.* **2008**, *19*, 111–116.
11. Ben-Haida, A.; Colquhoun, H. M.; Hodge, P.; Lewis, D. F. Reduction of carbonyl groups in aromatic polyketones: synthesis and characterization of methylene-bridged polyaryl-ethers and -thioethers. *Polymer* **1999**, *40*, 5173–5182.
12. Díez-Pascual, A. M.; Martínez, G.; Gómez, M. A. Synthesis and characterization of poly(ether ether ketone) derivatives obtained by carbonyl reduction. *Macromolecules* **2009**, *42*, 6885–6892.
13. Manolakis, I.; Cross, P.; Colquhoun, H. M. Direct Iminization of PEEK. *Macromolecules* **2011**, *44*, 7864–7867.

14. Colquhoun, H. M.; Paoloni, F. P. V.; Drew, M. G. B.; Hodge, P. Dithioacetalisation of PEEK: a general technique for the solubilisation and characterisation of semi-crystalline aromatic polyketones. *Chem. Commun.* **2007**, 3365–3367.
15. Colquhoun, H. M.; Hodge, P.; Paoloni, F. P. V.; McGrail, P. T.; Cross, P. Reversible, nondegradative conversion of crystalline aromatic poly(ether ketone)s into organo-soluble poly(ether dithioketal)s. *Macromolecules* **2009**, *42*, 1955–1963.
16. Noiset, O.; Henneuse, C.; Schneider, Y. J.; Marchand-Brynaert, J. Surface reduction of poly(aryl ether ether ketone) film: UV spectrophotometric, ³H radiochemical, and X-ray photoelectron spectroscopic assays of the hydroxyl functions. *Macromolecules* **1997**, *30*, 540–548.
17. Fristrup, C. J.; Jankova, K.; Hvilsted, S. Hydrophilization of poly(ether ether ketone) films by surface-initiated atom transfer radical polymerization. *Polym. Chem.* **2010**, *1*, 1696–1701.
18. Chen, M.; Ouyang, L.; Lu, T.; Wang, H.; Meng, F.; Yang, Y.; Ning, C.; Ma, J.; Liu, X. Enhanced bioactivity and bacteriostasis of surface fluorinated polyetheretherketone. *ACS Appl. Mater. Interfaces* **2017**, *9*, 16825–16834.
19. Ruppert, I.; Schlich, K.; Volbach, W. Die ersten CF₃-substituierten organyl(chlor)silane. *Tetrahedron Lett.* **1984**, *25*, 2195–2198.
20. Prakash, G. K. S.; Krishnamurti, R.; Olah, G. A. Fluoride-induced trifluoromethylation of carbonyl compounds with trifluoromethyltrimethylsilane (TMS-CF₃). A trifluoromethide equivalent. *J. Am. Chem. Soc.* **1989**, *111*, 393–395.
21. Prakash, G. K. S.; Yudin, A. K. Perfluoroalkylation with organosilicon reagents. *Chem. Rev.* **1997**, *97*, 757–786.
22. Hirao, A.; Sugiyama, K.; Yokoyama, H. Precise synthesis and surface structures of architectural per- and semifluorinated polymers with well-defined structures. *Prog. Polym. Sci.* **2007**, *32*, 1393–1438.

23. Lüning, J.; Stöhr, J.; Song, K. Y.; Hawker, C. J.; Iodice, P.; Nguyen, C. V.; Yoon, D. Y. Correlation of surface and bulk order in low surface energy polymers. *Macromolecules* **2001**, *34*, 1128–1130.
24. Borkar, S.; Jankova, K.; Siesler, H. W.; Hvilsted, S. New highly fluorinated styrene-based materials with low surface energy prepared by ATRP. *Macromolecules* **2004**, *37*, 788–794.
25. Discekici, E. H.; Anastasaki, A.; Kaminker, R.; Willenbacher, J.; Truong, N. P.; Fleischmann, C.; Oschmann, B.; Lunn, D. J.; de Alaniz, J. R.; Davis, T. P.; Bates, C. M.; Hawker, C. J. Light-mediated atom transfer radical polymerization of semi-fluorinated (meth)acrylates: facile access to functional materials. *J. Am. Chem. Soc.* **2017**, *139*, 5939–5945.
26. Ishizone, T.; Sugiyama, K.; Sakano, Y.; Mori, H.; Hirao, A.; Nakahama, S. Anionic polymerizations of perfluoroalkyl methacrylates and synthesis of well-defined ABC triblock copolymers of methacrylates containing hydrophilic, hydrophobic, and perfluoroalkyl groups. *Polym. J.* **1999**, *31*, 983–988.
27. Hunt Jr, M. O.; Belu, A. M.; Linton, R.W.; DeSimone, J. M. End-functionalized polymers. 1. Synthesis and characterization of perfluoroalkyl-terminated polymers via chorosilane derivatives. *Macromolecules* **1993**, *26*, 4854–4859.
28. Sugiyama, K.; Hirao, A.; Nakahama, S. Synthesis of end-functionalized polymer by means of living anionic polymerization, 7: reaction of anionic living polymers with perfluoroalkyl halides. *Macromol. Chem. Phys.* **1996**, *197*, 3149–3165.
29. McHugh, M. A.; Park, I-H.; Reisinger, J. J.; Ren, Y.; Lodge, T. P.; Hillmyer, M. A. Solubility of CF₂-modified polybutadiene and polyisoprene in supercritical carbon dioxide. *Macromolecules* **2002**, *35*, 4653–4657.
30. Hillmyer, M. A.; Schmuhl, N. W.; Lodge, T. P. Fluorinated amphiphilic block copolymers: combining anionic polymerization and selective polymer modification. *Macromol. Symp.* **2004**, *215*, 51–56.

31. Staniland, P. A., "Poly(ether ketone)s". In *Comprehensive Polymer Science*; Allen, G.; Bevington, J. C., Ed. Pergamon: Oxford, **1989**; Vol. 5, 483-497.
32. Bryant, R. G.; Jensen, B. J.; Hergenrother, P. M. Synthesis and properties of phenylethynyl-terminated arylene ethers. *Polym. Prepr. (Am. Chem. Soc., Div. Polym. Chem.)* **1992**, 33, 910-911.
33. Gardner, K. H.; Hsiao, B. S.; Matheson, R. R.; Wood, B. A. Structure, crystallization and morphology of poly(aryl ether ketone ketone). *Polymer* **1992**, 33, 2483–2495.
34. Li, Y.; Pham, J. Q.; Johnston, K. P.; Green, P. F. Contact angle of water on polystyrene thin films: effects of CO₂ environment and film thickness. *Langmuir* **2007**, 23, 9785–9793.
35. Investigation of Plasma Treatment on Micro-Injection Moulded Microneedle for Drug Delivery. Nair, K.; Whiteside, B.; Grant, C.; Patel, R.; Tuinea-Bobe, C.; Norris, K.; Paradkar, A. *Pharmaceutics*, **2015**, 7, 471–485.
36. Yasuda, H.; Sharma, A. K.; Yasuda, T. Effect of orientation and mobility of polymer molecules at surfaces on contact angle and its hysteresis. *J. Polym. Sci. Part B. Polym. Phys.* **1981**, 19, 1285–1291.

FOR TABLE OF CONTENTS USE ONLY

Trifluoromethylation of carbonyl groups in aromatic poly(ether ketone)s: formation of strongly polar yet surface-hydrophobic poly(arylenecarbinol)s

*Flavien Leroux, Roger A. Bennett, David F. Lewis and Howard M. Colquhoun**

Department of Chemistry, University of Reading, Whiteknights, Reading, RG6 6AD, UK

TOC Graphic

